



Controlled suppression of superconductivity by the generation of polarized Cooper pairs in spin-valve structures

M. G. Flokstra,^{1,*} T. C. Cunningham,¹ J. Kim,² N. Satchell,² G. Burnell,² P. J. Curran,³ S. J. Bending,³ C. J. Kinane,⁴ J. F. K. Cooper,⁴ S. Langridge,⁴ A. Isidori,⁵ N. Pugach,^{5,6} M. Eschrig,⁵ and S. L. Lee¹

¹*School of Physics and Astronomy, SUPA, University of St. Andrews, St. Andrews KY16 9SS, United Kingdom*

²*School of Physics and Astronomy, University of Leeds, Leeds LS2 9JT, United Kingdom*

³*Department of Physics, University of Bath, Claverton Down, Bath BA2 7AY, United Kingdom*

⁴*ISIS, Rutherford Appleton Laboratory, Oxfordshire OX11 0QX, United Kingdom*

⁵*SEPnet and Hubbard Theory Consortium, Department of Physics, Royal Holloway, University of London Egham, Surrey TW20 0EX, United Kingdom*

⁶*Skobel'syn Institute of Nuclear Physics Lomonosov Moscow State University (SYNP MSU), Leninskie Gory, Moscow 119991, Russia*
(Received 10 April 2014; revised manuscript received 13 January 2015; published 2 February 2015)

Transport measurements are presented on thin-film superconducting spin-valve systems, where the controlled noncollinear arrangement of two ferromagnetic Co layers can be used to influence the superconducting state of Nb. We observe a very clear oscillation of the superconducting transition temperature with the relative orientation of the two ferromagnetic layers. Our measurements allow us to distinguish between the competing influences of domain averaging, stray dipolar fields, and the formation of superconducting spin triplets. Domain averaging is shown to lead to a weak enhancement of transition temperature for the antiparallel configuration of exchange fields, while much larger changes are observed for other configurations, which can be attributed to drainage currents due to spin triplet formation.

DOI: [10.1103/PhysRevB.91.060501](https://doi.org/10.1103/PhysRevB.91.060501)

PACS number(s): 74.45.+c, 74.25.F-, 74.78.Fk, 74.81.-g

The normally antagonistic ground states of conventional superconductivity and ferromagnetism give rise to a variety of intriguing phenomena when brought into close proximity, a subject that has gained much attention both theoretically [1–9] and experimentally [10–18] over recent years. The underlying proximity effect of singlet Cooper pairs penetrating a ferromagnetic (F) layer is nonmonotonic in nature, which is very different from the monotonic decay found for the case of proximity coupling into a normal (N) metal. This unconventional proximity effect leads, for example, to oscillations in the critical temperature (T_c) of the superconductor as function of the thickness of the F layer [19–21].

In 2002 the superconducting spin valve was proposed theoretically [22,23], comprising a superconducting (S) spacer layer separating two F layers. For ideal operation, the supercurrent in the S layer can be controlled by switching the relative orientation of the exchange fields (H_{ex}) of the F layers from a parallel (P) to an antiparallel (AP) alignment. The underlying physical mechanism involves the interaction of the singlet Cooper pair with both exchange fields, whereby it experiences an additional pair dephasing if the device is in the P state, due to a potential energy mismatch between the spin up and spin down electron of the penetrated pair, thus lowering T_c . Such an effect does not occur in the AP case, since both electrons find themselves in equivalent bands. This mechanism can be generalized as a relative enhancement of T_c by domain averaging and has been observed in a variety of experiments [24–28], where, with the exception of Ref. [25], a *pinned* magnetic layer is used to create the AP arrangement. However, several seemingly anomalous results with precisely the opposite behavior have also been reported [29–33]. One plausible explanation proposed for these results, in systems

where no pinning layer was used, is the dominance of a suppression of superconductivity by dipolar fields generated by the domains [25]. In experimental work caution therefore needs to be exercised to avoid a dominant contribution from dipolar fields and to be aware that inhomogeneous magnetism (on the length scale of the superconducting coherence length) inherently includes enhancement by domain averaging.

The already rich ground state in S/F proximity coupled systems becomes even more exotic when noncollinear alignments of the exchange fields are considered. Equal spin triplet pair correlations emerge from the condensate when experiencing inhomogeneous magnetism [1,3–7]. Not being an eigenstate of the superconducting condensate, these triplets, unlike singlets, are not antagonistic to the ferromagnetic ground state and typically penetrate over a much longer distance into F layers (comparable to the case of N). This leads to an enhanced drainage of Cooper pairs from the superconductor and thus to a suppression of the superconducting state [8]. It was shown theoretically that the density of these spin triplets scales with the magnitude of H_{ex} and one should use strong ferromagnets to observe this suppression. There are several experiments where the presence of equal spin triplet pairs have been reported [12–16] but the generation processes are not fully understood, and are not always well controlled experimentally. Experimental data on S/F proximity systems for noncollinear magnetization are vital to better understand these systems and to aid theory towards improved modeling. Some results have been reported on pinned spin-valve type systems [24,26–28,34–36], including angular rotation [35,36], but to date none have shown an unambiguous suppression of T_c due to the noncollinearity of the F elements. Most recently experiments on a related exchange spring system showed results that appear to contradict the predictions of theory in the weak limit [37].

*Corresponding author: mgf@st-andrews.ac.uk

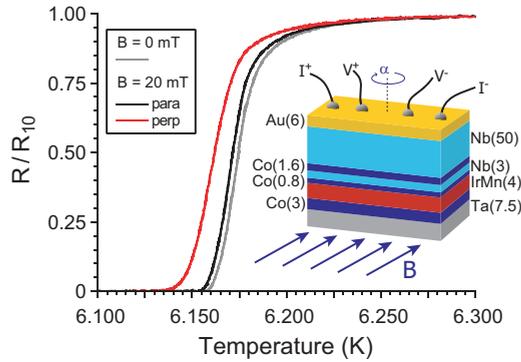


FIG. 1. (Color online) Normalized resistance of the *SFF* sample A as a function of temperature for $B = 0$ (right), $B = 20$ mT parallel to the pinning direction (middle), $B = 20$ mT perpendicular to the pinning direction (left). Inset: Schematic for the *SFF* structure (sample A).

In this Rapid Communication we present transport measurements on Nb/Co based spin-valve systems in which we explore the effect of noncollinear exchange fields on the superconducting state. Our devices were designed and characterized so as to minimize domain formation and quantify the influence of stray fields, which enables us to disentangle the observed enhancement of T_c from domain averaging and the suppression by spin triplet drainage. We observe a *large* monotonic increase in the suppression of the superconducting state with an increased level of magnetic inhomogeneity, while at collinear angles we recover the established result of the domain averaging effect with an effective T_c shift between the P and AP state of a few mK. These results are in strong agreement with theoretical expectations for a suppression of T_c with noncollinearity due to the generation of equal spin triplets.

We present data on two types of spin valves, one with the *S* layer separating the two *F* layers (*FSF*) and one with the *S* layer on top (*SFF*) (see the inset of Fig. 1). For both architectures, the top *F* layer is the free layer where the magnetization direction is easily manipulated by a small external field, while in the bottom *F* layer the magnetization direction is exchange biased and hence pinned by an adjacent layer of antiferromagnetic IrMn [see Supplemental Material (SM) Sec. 1.1 [38]]. Samples were prepared by dc magnetron sputtering on Si (100) substrates in a system with a base pressure of 10^{-8} mbar at ambient temperature and in a single vacuum cycle. Growth was undertaken at a typical Ar flow of 24 sccm and pressure of $2-3 \mu\text{bar}$ at a substrate-sample distance of approximately 25 mm, with a typical growth rate of 0.2 nm s^{-1} . Growth rates for each material were calibrated using fits to the Kiessig fringes in low angle x-ray reflectivity measurements. All layers were sputtered in the presence of a homogeneous magnetic field at the sample in order to establish the pinning. The full stacking sequence for the *SFF* spin valve (sample A) is Au(6)/Nb(50)/Co(1.6)/Nb(3)/Co(0.8)/IrMn(4)/Co(3)/Ta(7.5)/Si substrate (inset of Fig. 1), with numbers indicating layer thicknesses in nm. The Ta buffer layer is to improve growth quality, the adjacent Co buffer layer is to determine the direction of the pinning for the IrMn, and the next Co layer is the actual pinned active layer. The free Co layer is separated from the active pinned Co layer by a thin Nb

decoupling layer that is nonsuperconducting. The superconducting Nb layer is next to the free Co layer, and the sample is capped with a thin protective layer to prevent oxidation. The *FSF* sample (sample B) has Au(6)/Co(2.4)/Nb(50)/Co(1.2)/IrMn(4)/Co(3)/Ta(7.5)/Si substrate; a second *SFF* structure (sample C) with Co layers with identical thicknesses to this *FSF* was also measured. All Co layers have the easy axis in the plane of the film.

Transport measurements on samples of roughly $10 \text{ mm} \times 3 \text{ mm}$ were performed using a standard four-point geometry in a helium flow cryostat cooled via exchange gas. An external magnet provides a very homogeneous field at the sample. The cryostat itself is mounted such that it can be rotated around its vertical axis, controlled by a stepper motor. Typical rotation speeds used were about 0.04 rad/s . Figure 1 shows a typical transition curve for our devices in zero field (with resistance normalized to the resistance at $T = 10 \text{ K}$) with a T_c of around 6.2 K . Magnetization characterization measurements were performed in a commercial superconducting quantum interference device (SQUID) magnetometer (Quantum Design MPMS-XL) mainly to determine the switching behavior of the layers. In addition, the stray field for different configurations of the *F* layers in the *S* layer was quantified using a scanning Hall-probe (SHP) technique, using the microscope described in Ref. [39] (see SM Sec. 2.1 [38]).

To characterize the magnetic switching properties of our spin valves we first examine a control sample containing only the pinning part of the full device (i.e., omitting the *S* and free *F*). Results of SQUID measurements are shown in the inset of Fig. 2 for the bias (pinning) direction both parallel and perpendicular to the applied field direction of the SQUID. In the parallel case, a clear exchange biased hysteresis curve is obtained with a bias field of around 46 mT , which is associated with the buffer Co layer. The thinner, active pinned layer is much more strongly exchange biased and a slow closing tail is present in the hysteresis curve for negative fields which closes at about -250 mT (SM Fig. 6 [38]). A very different

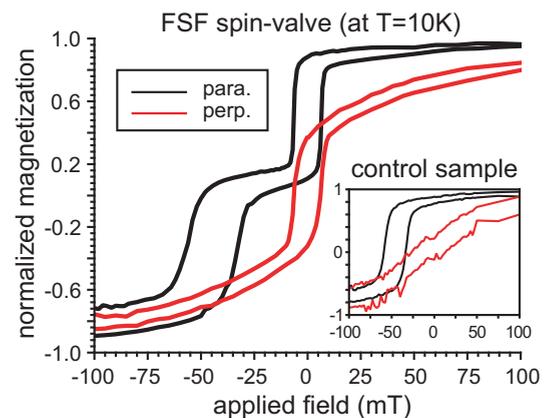


FIG. 2. (Color online) Magnetization measurements on the full *FSF* spin-valve structure (sample B) as a function of applied field H_a for (black) H_a parallel to the pinning direction and (red) H_a perpendicular to the pinning direction. Inset: Magnetization measurements on a control sample comprising only a pinned magnetic layer, as a function of applied field H_a for (black) H_a parallel to the pinning direction and (red) H_a perpendicular to the pinning direction.

response is observed in the perpendicular configuration where no traces of any form of exchange biasing are seen. Note that the tail part is very similar for both relative orientations. The perpendicular case can be fitted with a simple Stoner-Wohlfarth model for coherent rotation, including two fixed Zeeman terms to describe the exchange bias fields of the two layers, with one bias around 45 mT and one around 200 mT.

Figure 2 also shows similar magnetization measurements for the full *FSF* spin-valve geometry (sample B). For both orientations the result is similar to the control sample, with a hysteretic exchange bias of 46 mT and a slow closing tail, but now with an added unbiased hysteretic part with switching fields of ± 6 mT. This corresponds to the response of the free Co layer. The additional fractional change of the total magnetization is consistent with the fractional Co thickness of the top *F* layer. The alternative *SFF* spin valves (samples A and C) have almost identical characteristics.

For the rotation transport measurements we used a fixed external field, typically 16–21 mT, chosen such that it exceeds the switching field of the free *F* layer but is still well below the exchange bias field of the pinned layers. The sample is rotated with the rotation axis normal to the sample plane. To further investigate how much stray field is generated under these conditions, we performed SHP measurements, which are sensitive to components of magnetic field perpendicular to the surface of the film. Considering a structure comprising *only* the pinned layer, at a measurement field of ~ 10 mT, a weak magnetic texture can be observed with a stray field of less than 0.1 mT. At 77 K this texture is found to be *totally unchanged* by rotation of the magnetic field between 0° and 90° to the pinning direction (SM Sec. 2.2 [38]). The full *SFF* structure (sample A) was also investigated at 10 mT and at a temperature below the T_c of the superconducting layer. Here once again *no variation with angle* of the stray field and magnetic texture was observed for relative orientations of the field to the pinning direction of 0° and 90° (SM Sec. 2.2 [38]). We thus conclude that under the conditions in which the transport experiments were undertaken, there is little contribution from dipolar fields in the superconducting layer, but more importantly, that there is a negligible influence on the superconducting state of the dipolar-field contributions as a *function of angle*. The results are consistent with a single domain type of rotation of the free layer, while both of the Co layers adjacent to the IrMn layer remain effectively pinned along the bias direction. For an applied field of 21 mT rotating in the plane of the film, for arbitrary angle the magnetization of the free layer will always be parallel to the external applied field, while the (average) magnetization of the pinned layers will be coherently tilted by a very small angle away from the pinning direction. At this field one can consider the exchange field in the pinned layer always to be effectively parallel to the pinning direction.

Resistance measurements were taken at various positions along the superconducting transition curve as functions of the angle α between the external field and the bias direction. The sample was mounted such that the P state corresponds to $\alpha = 0^\circ$ and the AP state to $\alpha = 180^\circ$. All curves presented are measured over a range of 720° , with an average over two repeat scans in each direction. The voltage noise was found to be dominated by temperature fluctuations which were typically below ~ 1 mK. Figure 3 shows results on the *SFF* spin valve

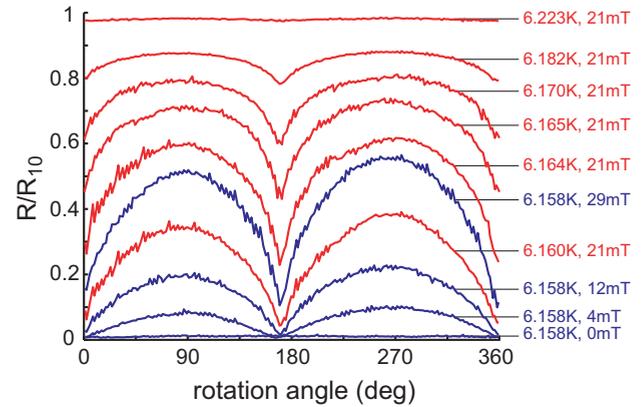


FIG. 3. (Color online) Normalized resistance measurements on the *SFF* spin-valve structure (sample A) as a function of the angle between the external field and the exchange bias direction, for various temperatures and fields along the transition curve.

(sample A) at different temperatures along the transition curve (the resistance is normalized to the resistance at $T = 10$ K). A very clear oscillatory dependence of the resistance as function of α is seen. There are minima near the collinear angles (0° and 180°), where the exchange fields are either parallel or antiparallel to each other, and there are maxima near the perpendicular angles (90° and 270°) where those fields are effectively perpendicular. The curves approximately follow a $\sqrt{|\sin \alpha|}$ dependence.

Figure 4 shows similar measurements on the *FSF* structure (sample B) and a second *SFF* structure (sample C) with thicker Co layers, 2.4 and 1.2 nm for the free and active pinned layer, respectively. For both structures the data are qualitatively similar to Fig. 3, but for the *SFF* structure with thicker Co layers the oscillations are of smaller amplitude. For temperatures near the steepest parts of the transition curves we can also clearly capture the difference between P and AP alignment at the collinear angles for both sample types (also

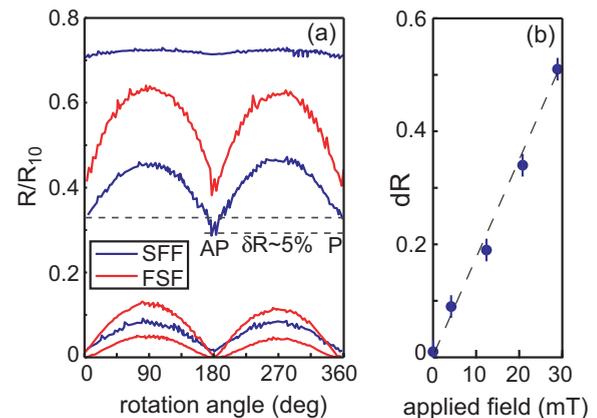


FIG. 4. (Color online) (a) Normalized resistance measurements on the *FSF* (sample B) and a second *SFF* spin-valve structure (sample C) as a function of the angle between the external field and the exchange bias direction, for various temperatures along the transition curve. (b) The resistance change dR between $\alpha = 0^\circ$ and $\alpha = 90^\circ$ induced in the *SFF* sample A at 6.158 K by increasing the applied field.

present in Fig. 3). We find a maximum relative resistance difference of about 0.05, which for our typical devices with a transition width of about 50 mK means a corresponding T_c shift of about 2–3 mK (a rather well established result for many spin valves). This effect is in agreement with theoretical predictions of a slight lowering of T_c for the P state.

The more striking result in the present measurements is the much *larger* shifts in T_c observed for all samples due to the *noncollinearity* of the magnetic layers. This can already be clearly seen in the $R(T)$ curves of Fig. 1 (see also SM Fig. 7 [38]). Theoretically, the presence of the noncollinear magnetization provides a mechanism to increase the conversion of singlet Cooper pairs into the triplet channel, as has now been observed in a number of experiments involving coherent transport of triplet correlations through a ferromagnetic layer [12–16]. Viewed from the perspective of the singlet superconductor, this represents a “drainage” current that partially suppresses the superconducting order parameter and hence lowers T_c . Our data are thus in good agreement with these theoretical expectations. Considering the measurements undertaken at 6.158 K for *SFF* sample A (Fig. 3), although there is no angular dependence in zero field, the resistance can be smoothly increased from zero with both field angle and *value of applied field*, indicating a *highly tunable* resistance [Fig. 4(b)], which may reflect the polarizing influence of the field on equal spin triplets. This result demonstrates the feasibility of a field-controlled source of equal spin triplets, since it is the drainage to the triplet channel that suppresses the singlet fraction and reduces T_c .

We compare our results to a related experiment recently reported on an Nb-Py system, where a Sm-Co exchange spring is used to induce a noncollinear twist in the magnetization of the Py layer, similar to a Bloch wall [37]. Here the degree of rotation inside the Py layer is controlled by the angle of the applied field to the Sm-Co pinning direction. In that work a result is obtained that is superficially opposite to ours. They observe a nonmonotonic dependence of applied field with angle that has maxima in the resistivity at 0° and 180° and minima close to 106° and 286° . As in the present case, these also result from an electronic proximity, but in contrast to our measurements, the angular dependence appears contradictory to existing theory. We note, however, that in these experiments the analysis is complicated by the fact that

the superconductivity samples only a fraction of the magnetic spiral, and in addition there is a considerable lag between the applied field angle and the total twist angle of the spiral. By contrast, in our experiment the coherence length (~ 10 nm) is comparable to the length scale of the magnetic noncollinearity, and at the applied fields measured the field angle is essentially equal to the relative angle of the two exchange fields. It is interesting to note that in the exchange spring experiment a local maximum is observed at an applied field angle of $\theta = 180^\circ$, which the authors estimate corresponds to a total *noncollinearity* of around $\varphi \sim 90^\circ$, the angle at which we also observe a maximum. This would not of course explain the even larger maximum at $\varphi = 0^\circ$ present in their data, but it may be the case that in such a complex magnetic arrangement as an exchange spring that there are competing influences on the superconducting state. We therefore hope that the very clear results that we present on our much simpler system may help theoretical understanding of these other interesting experiments.

In conclusion, we have observed a dependence of the superconducting transition temperature for two different types of Co-Nb spin valves. For both sample types (*SFF* and *FSF*) a large suppression of T_c is found when the exchange fields are orthogonal, consistent with the theoretical expectations for the drainage of singlets into the triplet channel when the magnetization is noncollinear. This suppression may also be controlled by the magnitude of the applied field. In both structures T_c is a maximum (resistance a minimum) for an AP alignment, with a marginally less pronounced maximum in T_c for the P case, consistent with the theoretical weak limit result. These results provide a clear and convincing validation of existing theory. Moreover, since the system is relatively simple, it provides a useful framework in which to understand experimental data in more complex systems where theoretical predictions appear to be contradicted.

We acknowledge the support of the EPSRC through Grants No. EP/J01060X, No. EP/J010626/1, No. EP/J010650/1, No. EP/J010634/1, and No. EP/J010618/1, support of a studentship supported by JEOL Europe and the ISIS Neutron and Muon Source, and the support of the RFBR via Awards No. 13-02-01452-a, and No. 14-02-90018 BEL-a.

-
- [1] A. I. Buzdin, *Rev. Mod. Phys.* **77**, 935 (2005).
 - [2] Ya. V. Fominov, A. A. Golubov, and M. Yu. Kupriyanov, *JETP Lett.* **77**, 510 (2003).
 - [3] F. S. Bergeret, A. F. Volkov, and K. B. Efetov, *Phys. Rev. B* **69**, 174504 (2004).
 - [4] F. S. Bergeret, A. F. Volkov, and K. B. Efetov, *Rev. Mod. Phys.* **77**, 1321 (2005).
 - [5] T. Löfwander, T. Champel, J. Durst, and M. Eschrig, *Phys. Rev. Lett.* **95**, 187003 (2005).
 - [6] M. Houzet and A. I. Buzdin, *Phys. Rev. B* **76**, 060504(R) (2007).
 - [7] M. Eschrig and T. Löfwander, *Nat. Phys.* **4**, 138 (2008).
 - [8] Ya. V. Fominov, A. A. Golubov, T. Yu. Karminskaya, M. Yu. Kupriyanov, R. G. Deminov, and L. R. Tagirov, *JETP Lett.* **91**, 308 (2010).
 - [9] C.-T. Wu, O. T. Valls, and K. Halterman, *Phys. Rev. B* **86**, 014523 (2012).
 - [10] T.-Kontos, M. Aprili, J. Lesueur, F. Genêt, B. Stephanidis, and R. Boursier, *Phys. Rev. Lett.* **89**, 137007 (2002).
 - [11] V. V. Ryazanov, V. A. Oboznov, A. Yu. Rusanov, A. V. Veretennikov, A. A. Golubov, and J. Aarts, *Phys. Rev. Lett.* **86**, 2427 (2001).

- [12] R. S. Keizer, S. T. B. Goennenwein, T. M. Klapwijk, G. Miao, G. Xiao, and A. Gupta, *Nature (London)* **439**, 825 (2006).
- [13] J. W. A. Robinson, J. D. S. Witt, and M. G. Blamire, *Science* **329**, 59 (2010).
- [14] D. Sprungmann, K. Westerholt, H. Zabel, M. Weides, and H. Kohlstedt, *Phys. Rev. B* **82**, 060505(R) (2010).
- [15] T. S. Khaire, M. A. Khasawneh, W. P. Pratt, Jr., and N. O. Birge, *Phys. Rev. Lett.* **104**, 137002 (2010).
- [16] M. S. Anwar, M. Veldhorst, A. Brinkman, and J. Aarts, *Appl. Phys. Lett.* **100**, 052602 (2012).
- [17] R. I. Salikhov, I. A. Garifullin, N. N. Garif'yanov, L. R. Tagirov, K. Theis-Bröhl, K. Westerholt, and H. Zabel, *Phys. Rev. Lett.* **102**, 087003 (2009).
- [18] J. Xia, V. Shelukhin, M. Karpovski, A. Kapitulnik, and A. Palevski, *Phys. Rev. Lett.* **102**, 087004 (2009).
- [19] Z. Radović, M. Ledvij, L. Dobrosavljević-Grujić, A. I. Buzdin, and J. R. Clem, *Phys. Rev. B* **44**, 759 (1991).
- [20] J. S. Jiang, D. Davidović, D. H. Reich, and C. L. Chien, *Phys. Rev. Lett.* **74**, 314 (1995).
- [21] C. L. Chien, J. S. Jiang, J. Q. Xiao, D. Davidović, and D. H. Reich, *J. Appl. Phys.* **81**, 5358 (1997).
- [22] L. R. Tagirov, *Phys. Rev. Lett.* **83**, 2058 (1999).
- [23] A. I. Buzdin, A. V. Vedyayev, and N. V. Ryzhanova, *Europhys. Lett.* **48**, 686 (1999).
- [24] J. Y. Gu, C.-Y. You, J. S. Jiang, J. Pearson, Ya. B. Bazaliy, and S. D. Bader, *Phys. Rev. Lett.* **89**, 267001 (2002).
- [25] A. Yu. Rusanov, M. Hesselberth, J. Aarts, and A. I. Buzdin, *Phys. Rev. Lett.* **93**, 057002 (2004).
- [26] A. Potenza and C. H. Marrows, *Phys. Rev. B* **71**, 180503(R) (2005).
- [27] I. C. Moraru, W. P. Pratt, Jr., and N. O. Birge, *Phys. Rev. Lett.* **96**, 037004 (2006).
- [28] I. C. Moraru, W. P. Pratt, Jr., and N. O. Birge, *Phys. Rev. B* **74**, 220507(R) (2006).
- [29] A. Yu. Rusanov, S. Habraken, and J. Aarts, *Phys. Rev. B* **73**, 060505(R) (2006).
- [30] R. Steiner and P. Ziemann, *Phys. Rev. B* **74**, 094504 (2006).
- [31] D. Stamopoulos, E. Manios, and M. Pissas, *Phys. Rev. B* **75**, 184504 (2007).
- [32] G. Carapella, F. Russo, and G. Costabile, *Phys. Rev. B* **78**, 104529 (2008).
- [33] M. Flokstra, J. M. van der Knaap, and J. Aarts, *Phys. Rev. B* **82**, 184523 (2010).
- [34] V. I. Zdravkov, J. Kehrle, G. Obermeier, D. Lenk, H.-A. Krug von Nidda, C. Müller, M. Yu. Kupriyanov, A. S. Sidorenko, S. Horn, R. Tidecks, and L. R. Tagirov, *Phys. Rev. B* **87**, 144507 (2013).
- [35] J. Zhu, I. N. Krivorotov, K. Halterman, and O. T. Valls, *Phys. Rev. Lett.* **105**, 207002 (2010).
- [36] P. V. Leksin, N. N. Garif'yanov, I. A. Garifullin, Ya. V. Fominov, J. Schumann, Y. Krupskaya, V. Kataev, O. G. Schmidt, and B. Büchner, *Phys. Rev. Lett.* **109**, 057005 (2012).
- [37] L. Y. Zhu, Y. Liu, F. S. Bergeret, J. E. Pearson, S. G. E. te Velthuis, S. D. Bader, and J. S. Jiang, *Phys. Rev. Lett.* **110**, 177001 (2013).
- [38] See Supplemental Material at <http://link.aps.org/supplemental/10.1103/PhysRevB.91.060501> for a detailed description of sample fabrication and additional characterization, including a description of experimental techniques.
- [39] V. V. Khotkevych, M. V. Milosević, and S. J. Bending, *Rev. Sci. Instrum.* **79**, 123708 (2008).